

pH, Calcium and Hydroxyl Ions Released from Nanoparticle Calcium Hydroxide as Intracanal Medicament

Atia Nurul Sidiqa^{1,2}, Dhiya Salsabila², Intan Wijayanthi², Ira Artilia³, Myrna Nurlatifah Zakaria^{4,5*}, I Made Joni^{6,7}, Ani Melani Maskoen^{2,8}

1. Doctoral Study Program, Faculty of Medicine, Universitas Padjadjaran, Bandung, West Java, Indonesia.
2. Faculty of Dentistry, Universitas Jenderal Achmad Yani, Jl Terusan Jenderal Sudirman, Cimahi 40285, Indonesia.
3. Department of Dental Materials Science and Technology, Faculty of Dentistry, Universitas Jenderal Achmad Yani, Jl Terusan Jenderal Sudirman, Cimahi 40285, Indonesia.
4. Department of Endodontology and Operative Dentistry, Faculty of Dentistry, Universitas Jenderal Achmad Yani, Cimahi, 40513, Indonesia.
5. Department of Restorative Dentistry, Faculty of Dentistry, Universiti Malaya, Kuala Lumpur 50603, Malaysia.
6. Department of Physics, Faculty of Mathematics and Natural Sciences, Universitas Padjadjaran, Sumedang 45363, Indonesia.
7. Functional Nano Powder University Center of Excellence, Universitas Padjadjaran, Sumedang 45363, Indonesia.
8. Department of Oral Biology, Faculty of Dentistry, Universitas Padjadjaran, Sumedang 45363, Indonesia.

Abstract

Ca(OH)₂ has an antimicrobial effect through the dissociation of Ca²⁺, OH⁻ ion and pH ideally used as an intracanal medicament. Nanoparticle Ca(OH)₂ has been successfully obtained from natural limestone in Indonesia. Nanoparticle Ca(OH)₂, aquades, propylene glycol (PG), methylcellulose (MS) and barium sulfate (BS) formulations can affect the mechanism of action.

This study aims to determine the effectiveness of the Ca(OH)₂ nanoparticle formula as an intracanal medicament through the Ca²⁺, OH⁻ ion release and pH at the evaluation on days 1, 7, and 14. The method of this study was an experimental study consisting of two groups, the first group is the nanoparticle Ca(OH)₂ 25%, aquades, PG 3%, MS 2% and BS 35% and Ca(OH)₂ Calxipex II® (Nippon Sika-Yakuhin., Shimonoseki, Japan) as the control group. Samples were inserted into polyethylene tubes and immersed with 10 mL of distilled water, incubated at 37°C and 100% humidity. Evaluation of Ca²⁺, OH⁻ ion release and pH has done with a spectrophotometer (Dirui DR-7000D, China) and a pH meter (Lutron/pH-207, Taiwan). The results showed the Ca²⁺ ion release in all groups increased to its peak on day 14 (11.29±0.196) mg/dL and (17.52±4.67) mg/dL.

The pH levels of the nanoparticle Ca(OH)₂ formula have the same pattern and are increased until day 14. However, this is not the same as measuring OH⁻ ion release. The number of OH⁻ ions released was highest on day 7 and decreased on day 14. There were significant differences between the two study groups on the measurements of the Ca²⁺, OH⁻ ion release and pH with different day variables. The commercial Ca(OH)₂ group demonstrated significantly higher levels of Ca²⁺, OH⁻ ion release and pH than the nanoparticle Ca(OH)₂ group. This can occur due to several factors that are affected, such as the solvent, powder-liquid ratio, particle size, and contaminations.

Experimental article (J Int Dent Med Res 2023; 16(3): 1061-1066)

Keywords: Ion release, calcium hydroxide, nanoparticle.

Received date: 16 June 2023

Accept date: 21 July 2023

Introduction

Calcium hydroxide Ca(OH)₂ is a white powder with a molecular weight of 74.08.

*Corresponding author:

Myrna Nurlatifah Zakaria,
Department of Endodontology and Operative Dentistry,
Faculty of Dentistry, Universitas Jenderal Achmad Yani
Jl. Terusan Jenderal Sudirman PO BOX 148,
Cimahi, Indonesia.
E-mail: myrna.nurlatifah@lecture.unjani.ac.id

Chemically, Ca(OH)₂ is classified as an alkaline because it is a strong base (pH 12.5 - 12.8) with a solubility level of 1.2 g/L at 25 °C, when in contact with a solvent it will dissociate into Ca²⁺ ions and hydroxyl ions (OH⁻). Ca(OH)₂ is an effective intracanal medicament because it has broad-spectrum antimicrobial properties, is biocompatible with tissues, reduces periradicular inflammation and can stimulate hard tissue^{1,2}. As an intracanal medication, Ca(OH)₂ is also essential in cases of recurrent periapical tissue infections. The use of Ca(OH)₂ as an intracanal

medicament is well-known due to its antimicrobial effect through the dissociation of Ca^{2+} , and OH^- ion. Furthermore, due to their capacity to generate high pH, which is imparted to the surrounding environment, the biological and antiseptic effects of calcium hydroxide depend on alkalinity and calcium ion release and promote tissue mineralization. Through an irreversible enzymatic process, the high pH of $\text{Ca}(\text{OH})_2$ encourages the suppression of microbial growth². Another crucial characteristic of $\text{Ca}(\text{OH})_2$ is its capacity to encourage the inactivation of bacterial lipopolysaccharides found in gram-negative outer membrane bacteria³. The release of OH^- ions is primarily responsible for the rise in pH in the surrounding tissue when $\text{Ca}(\text{OH})_2$ is used as a root canal medicament⁴. One of the most crucial elements that determine how effective they are is the quantity of OH^- ions that are present at the application site.

Due to their extremely small size, nanoparticles have a greater surface-to-volume ratio than bigger particles. As a result, a larger percentage of their atoms are concentrated on their surface, which increases their reactivity and responsiveness to their surroundings⁵. This larger surface area enables better interaction with the environment, which opens up a wide range of applications in disciplines including environmental research and medicine. The use of nanoparticles as antibacterial agents is an important application. Because of their small size and high surface-to-volume ratio, nanoparticles can interact with microbial cells more effectively, resulting in higher antibacterial action. The antibacterial activity of nanoparticles is also greatly influenced by their charge density⁶.

The discovery of nanoparticle $\text{Ca}(\text{OH})_2$ from natural limestone in Indonesia presents a groundbreaking opportunity for revolutionizing endodontic treatments^{7,8}. Despite its promising potential, questions remain regarding the effectiveness of this new formulation when combined with other substances such as aquades, propylene glycol, methylcellulose, and barium sulfate. To fully unlock the potential of this innovative discovery, it is crucial to conduct thorough experimental studies. Therefore, this study aims to evaluate the Ca^{2+} , OH^- ion release and pH of a nanoparticle $\text{Ca}(\text{OH})_2$ formula and compare it to a commercial $\text{Ca}(\text{OH})_2$ product over 14 days. The results of this study will provide invaluable insights into the potential use

of nanoparticle $\text{Ca}(\text{OH})_2$ in endodontic treatments and could ultimately pave the way for more effective and efficient treatments for patients.

Materials and methods

This is a true experimental study using $\text{Ca}(\text{OH})_2$ as an intracanal medication to evaluate ions Ca^{2+} , OH^- , and pH specifically on days 1, 7, and 14. There were two research groups (Table 1). Commercial $\text{Ca}(\text{OH})_2$ paste (Calcipex II[®], Nippon Sika-Yakuhin, Shimonoseki, Japan) containing $\text{Ca}(\text{OH})_2$ 24% added with BaSO_4 24%; the other group with nanoparticle $\text{Ca}(\text{OH})_2$ Palimanan 25% paste added with BaSO_4 (Pudak Scientific, Indonesia) 25%; PG (DOW PuraGuard[™], USA) 3%; and MS 2%, 10 samples in each measurement group. The nanoparticle $\text{Ca}(\text{OH})_2$ powder was manipulated to form a paste and then put into a polyethylene tube with a diameter of 2x1 cm and immersed in a plastic vial filled with 10 mL of distilled water. The container was kept at a temperature of 37°C and a humidity level of 100%. Each sample was measured for the release of Ca^{2+} ions on day 1, day 7, and day 14 using a spectrophotometer (DIRUI DR-7000D, China). The pH measurement uses a pH meter that has previously been calibrated using a buffer solution with a pH of 7. The pH (Lutron / pH-207, Taiwan), measurement process is carried out by inserting the electrode into each solution from the sample group. After obtaining the pH value, the rate of OH^- ions release was calculated. The numerical data normality test was tested using the Shapiro-Wilks test with a follow-up test using the independent t-test.

| Component | Nanoparticle $\text{Ca}(\text{OH})_2$ (%wt) | Commercial $\text{Ca}(\text{OH})_2$ paste (%wt) |
|--------------------------|---|---|
| $\text{Ca}(\text{OH})_2$ | 25% | 24% |
| BaSO_4 | 25% | 24% |
| Aquades | 45% | 52% |
| Propylene glycol (PG) | 3% | - |
| Methylcellulose (MS) | 2% | - |


Table 1. Intracanal Medicament Composition.

Results

Ca Ion Release

Graph 1 illustrates the release of Ca^{2+} ions in the commercial $\text{Ca}(\text{OH})_2$ and nanoparticle $\text{Ca}(\text{OH})_2$ groups on day 1, day 7, and day 14. The nanoparticle $\text{Ca}(\text{OH})_2$ group showed a Ca^{2+}

ion release of (6.97 ± 0.741) mg/dL on day 1, (9.20 ± 0.573) mg/dL on day 7, and (11.29 ± 0.196) mg/dL on day 14. In comparison, the commercial Ca(OH)_2 group had a Ca^{2+} ion release of (12.00 ± 1.990) mg/dL on day 1, (15.63 ± 1.257) mg/dL on day 7, and (17.52 ± 4.669) mg/dL on day 14. Both groups gradually released Ca^{2+} ions throughout the 14 days, but the commercial Ca(OH)_2 group had a higher and more stable ability to release Ca^{2+} ions over time.

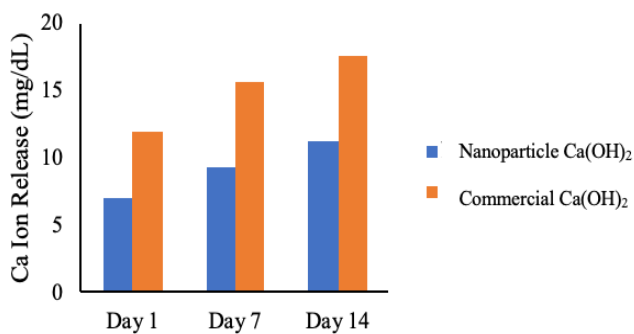

Graph 1. Release of Ca ion Release in commercial Ca(OH)_2 and Ca(OH)_2 nanoparticle groups.

| Ion Release Ca^{2+} (mg/dL) | Groups | | P value |
|--------------------------------------|--------------------------------|------------------------------|----------|
| | Nanoparticle Ca(OH)_2 | Commercial Ca(OH)_2 | |
| Day 1 | 6.97±0.741 | 12.00±1.990 | 0.001** |
| Day 7 | 9.20±0.573 | 15.63±1.257 | 0.0001** |
| Day 14 | 11.29±0.196 | 17.52±4.669 | 0.018** |


Table 2. Comparison between Ca^{2+} ion release on day 1, day 7, and day 14 in commercial Ca(OH)_2 and nanoparticle Ca(OH)_2 groups. *P value <0.05 which means statistically significant.

The average Ca^{2+} ion release was then analyzed using the Shapiro Wilks test as the results for the nanoparticle Ca(OH)_2 group obtained $p > 0.05$, which means that the data were normally distributed on day 1 and day 14; while on day 7, $p < 0.05$ means the data is not normally distributed. The normality test results in the commercial Ca(OH)_2 group had P values on day 1, day 7, and day 14 ($p > 0.05$), which means that the data were normally distributed as shown in Table 2.


The results of the study indicate that commercial Ca(OH)_2 released significantly higher amounts of Ca, hydroxide OH ions, and pH compared to nanoparticle Ca(OH)_2 over a period measured on days 1, 3, and 7, across all measurement categories.

Hydroxyl Ion Release

The commercial Ca(OH)_2 group had the highest levels of OH^- ion release on day 7 according to Graph 2: Overall, the commercial Ca(OH)_2 group had a higher rate of OH ion release than the nanoparticle Ca(OH)_2 . The release rate of OH ions increased for the commercial Ca(OH)_2 and nanoparticle Ca(OH)_2 formulations from day 1 to day 7, then it dropped on day 14. The measurements of OH ions in all groups revealed a release rate of OH ions on alkaline pH that was greater than 4.002×10^{-4} mol/L.

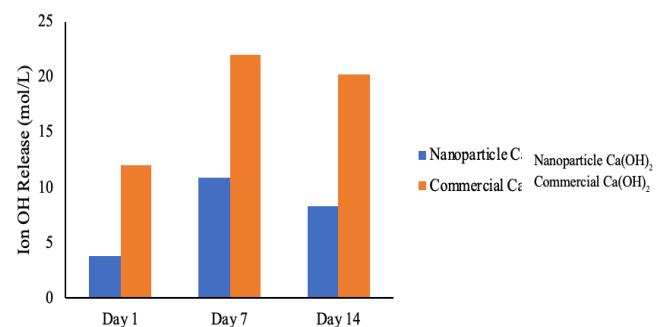

Graph 2. Hydroxyl Ion Release in Nanoparticle and Commercial Ca(OH)_2 .

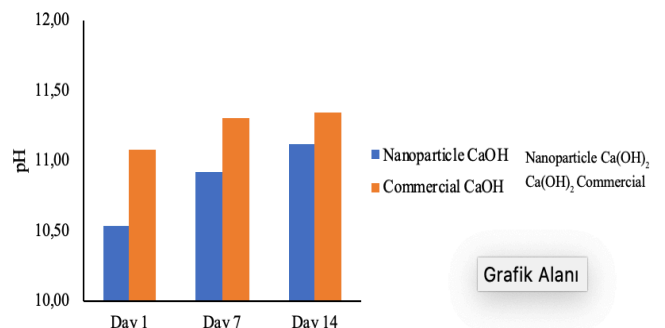

Graph 3. pH levels of two different types of Ca(OH)_2 .

pH Evaluation

Graph 3: shows the pH levels of two different types of Ca(OH)_2 over 14 days. The comparison pH levels of three different periods (day 1, day 7, and day 14) between two groups: the nanoparticle Ca(OH)_2 group and the commercial Ca(OH)_2 group. The nanoparticle Ca(OH)_2 group average pH on day 1 was (10.52 ± 0.214) , on day 7 it was (10.91 ± 0.316) , and on day 14, it was (11.11 ± 0.083) . The commercial Ca(OH)_2 group average pH on day 1 was (11.07 ± 0.058) , on day 7 was (11.29 ± 0.097) , and on day 14 was (11.34 ± 0.040) .

Discussion

In this study, there were two distinct groups of intracanal medicaments, each possessing unique compositions and formulations. The first group denoted Group 1, composed of nanoparticles Ca(OH)_2 obtained from Indonesian limestone, supplemented with propylene glycol (PG) and methylcellulose (MS) as thickening agents to ensure appropriate consistency. Meanwhile, the second group denoted Group 2, consists of Ca(OH)_2 with distilled water as a vehicle. Both groups were further characterized by the incorporation of BaSO_4 , which imparts a radiopacity, facilitating visualization in clinical settings. The careful characterization of these two groups using advanced techniques and meticulous measurements provides valuable insights into the role of these intracanal medicaments in endodontic practice. The findings of this study may serve as a basis for further research aimed at optimizing the formulation and delivery of intracanal medicaments to achieve enhanced clinical outcomes.

Calcium and hydroxide ions should be able to be released gradually and slowly in the optimum carrier⁹. The proposed vehicles are classified as aqueous and oily¹⁰. The conductivity of saturated calcium hydroxide solutions in distilled water and propylene glycol may reduce the effectiveness of calcium hydroxide as a root canal medicament¹¹. Additionally, the consistency of the PG enhances its handling properties and induces the most favourable release of Ca and hydroxyl ions compared to other vehicles. The sudden release of hydroxyl ions by the commercial Ca(OH)_2 group after 7 days can be attributed to the aqueous nature of DW, which promotes rapid ion release. This characteristic makes DW beneficial in clinical situations requiring short-term interappointment disinfection and in cases such as dental replantation and extreme exudative cases¹². The application of Ca(OH)_2 distilled water paste resulted in the faster and more significant release of Ca and OH ions. This difference may be caused by the different methodologies used as well as the addition of barium sulphate in these pastes¹³. The study revealed that the liberation of hydroxyl ions from propylene glycol as a vehicle exhibited its maximum concentration on day 7, with a

subsequent steady increase until day 14. This phenomenon can be attributed to the inherently high viscosity and limited solubility of propylene glycol, which lead to a gradual and protracted discharge of the hydroxyl ions¹⁴. Moreover, the incorporation of calcium hydroxide (Ca(OH)_2) and propylene glycol in medicament intracanal pastes demonstrated an enhancement in the calcium ion release kinetics¹⁵.

The low solubility and poor ability of BaSO_4 to diffuse make it difficult for oil paste containing calcium hydroxide compounds to reach maximum pH levels in a short period¹⁶. The results showed that intracanal medicament should be used for a minimum of 7 days to achieve maximum therapeutic effectiveness¹⁷. Barium sulphate (BaSO_4) in these pastes is added to increase radiopacity. Water-based radiopaque Ca(OH)_2 pastes with barium sulphate in ready to use paste form which could be easily cleaned and removed from the canal whenever required. Barium sulphate has better chemical stability and nondrying nature due to the ability of antibacterial and bacteriostatic^{18,19}.

Nanoparticles Ca(OH)_2 in aqueous suspensions structurally and morphologically with XRD and TEM, respectively and found that they were crystalline, regularly shaped, and hexagonally plated with dimensions 30 nm to 300 nm or less²⁰. Due to their extremely small size, nanoparticles have a greater surface-to-volume ratio than bigger particles. As a result, a larger percentage of their atoms are concentrated on their surface, which increases their reactivity and responsiveness to their surroundings⁶. This larger surface area enables better interaction with the environment, which opens up a wide range of applications in disciplines including environmental research and medicine. The use of nanoparticles as antibacterial agents is an important application²¹. Because of their small size and high surface-to-volume ratio, nanoparticles can interact with microbial cells more effectively, resulting in higher antibacterial action. The antibacterial activity of nanoparticles is also greatly influenced by their charge density. Furthermore, nanoparticles can also influence the pH of their environment, further enhancing their antimicrobial activity. By increasing the pH, nanoparticles can disrupt the membrane potential of microbial cells, causing further damage and leading to their destruction. Overall, the higher surface-to-volume ratio and charge density of

nanoparticles make them an excellent candidate for use as antimicrobial agents. These findings suggest that the use of commercial $\text{Ca}(\text{OH})_2$ may result in greater therapeutic efficacy due to its ability to release higher concentrations of these ions over an extended period. Through the use of cutting-edge techniques and rigorous statistical analysis, we have established a reliable dataset that can serve as a valuable resource for researchers and clinicians alike. We believe that this study contributes to the advancement of knowledge in the field of intracanal medicaments and has the potential to inform future directions of research in this area.

Conclusions

The results of the present study indicate that the release kinetics of Ca and OH ions, as well as pH, from $\text{Ca}(\text{OH})_2$ nanoparticles are inferior to those of commercial $\text{Ca}(\text{OH})_2$. Nevertheless, the observed biological activity of $\text{Ca}(\text{OH})_2$ nanoparticles highlights their potential as an antimicrobial agent, attributed to their ability to elevate pH levels via the release of Ca, OH, and pH ions. Consequently, $\text{Ca}(\text{OH})_2$ nanoparticles hold promise as an alternative to traditional intracanal medicaments in dentistry. The temporal profile of Ca, OH, and pH release revealed a periodic increase from day 1 to day 7, followed by a decline on day 14, with the peak levels of OH ion release observed on day 7.

Acknowledgements

This research was funded by Ministry of Education, Culture, Research, and Technology of the Republic of Indonesia with the Grant number: 041/SP2H/RT-MONO/LL4/2023; SPK/009/LPPMUNJANI/VII/2023.

Declaration of Interest

The authors report no conflict of interest.

References

1. Mohammadi Z, Dummer PMHH. Properties and applications of calcium hydroxide in endodontics and dentaltraumatology. *Int Endod J*. 2011;44(8):697-730. doi:10.1111/j.1365-2591.2011.01886.x
2. [Ba-Hattab R, Al-Jamie M, Aldreib H, Alessa L, Alonazi M. Calcium Hydroxide in Endodontics: An Overview. *Open J Stomatol*. 2016;06(12):274-289. doi:10.4236/ojst.2016.612033.
3. de Freitas RP, Greatti VR, Alcalde MP, Cavenago BC, Vivan RR, Duarte MAH, et al. Effect of the Association of Nonsteroidal Anti-inflammatory and Antibiotic Drugs on Antibiofilm Activity and pH of Calcium Hydroxide Pastes. *J Endod*. 2017;43(1):131-134. doi:10.1016/j.joen.2016.09.014
4. Zakaria MN, Siti Halimah IR, Sidiqa AN, Artilia I, Cahyanto A. Antimicrobial Activity of Calcium Hydroxide Synthesized from Indonesian Limestone against *Enterococcus faecalis*. *Materials Science Forum*. 2021;1044(August):171-177. doi:10.4028/www.scientific.net/MSF.1044.171
5. Hamouda. Current perspectives of nanoparticles in medical and dental biomaterials. *J Biomed Res*. 2012;26(3):143-151. doi:10.7555/JBR.26.20120027
6. Kandaswamy E, Nagendrababu V, Deivanayagam K. Antimicrobial effect of nanoparticles in endodontics. In: *Nanobiomaterials in Dentistry*. Vol 11. Elsevier; 2016:161-186. doi:10.1016/B978-0-323-42867-5.00015-1
7. Zakaria MN, Sidiqa AN, Artilia I, Cahyanto A. Synthesis and Characterization of Calcium Hydroxide from Indonesian Limestone as Endodontic Intracanal Medicament. *Key Eng Mater*. 2018;782:268-272. doi:10.4028/www.scientific.net/KEM.782.268
8. Artilia I, Sidiqa AN, Zakaria MN, Cahyanto A. Handling Property Improvement of Nano Calcium Hydroxide From Indonesian Limestone with Different Solvent Vehicles. *Journal of International Dental and Medical Research*. 2021;14(2):1-5.
9. Fulzele P, Baliga S, Thosar N, Pradhan D. Evaluation of calcium ion, hydroxyl ion release and pH levels in various calcium hydroxide based intracanal medicaments: An in vitro study. *Contemp Clin Dent*. 2011;2(4):291. doi:10.4103/0976-237X.91791
10. Athanassiadis B, Walsh LJ. Aspects of Solvent Chemistry for Calcium Hydroxide Medicaments. *Materials*. 2017;10(10):1219. doi:10.3390/ma10101219
11. Grover C, Shetty N. Evaluation of calcium ion release and change in pH on combining calcium hydroxide with different vehicles. *Contemp Clin Dent*. 2014;5(4):434. doi:10.4103/0976-237X.142803
12. Nadar A, Muliya V, Pai S, Pentapati K. A comparative evaluation of calcium ion release and pH change using calcium hydroxide nanoparticles as intracanal medicament with different vehicles – An in vitro study. *Journal of Conservative Dentistry*. 2023;26(1):47. doi:10.4103/jcd.jcd_387_22
13. Estrela C, Sydney GB, Figueiredo JAP, Estrela CR de A. Antibacterial efficacy of intracanal medicaments on bacterial biofilm: a critical review. *Journal of Applied Oral Science*. 2009;17(1):1-7. doi:10.1590/S1678-77572009000100002
14. Sidiqa AN, Hanif F, Zakaria MN, Artilia I, Cahyanto A. Setting Time of Calcium Hydroxide from Indonesian Limestone Paste with Various Solvent Vehicle for Intracanal Medicament. *Materials Science Forum*. 2021;1044:165-170. doi:10.4028/www.scientific.net/MSF.1044.165
15. Jain A, Bhadoria K, Hada HS, Singh Hada H. Spectrophotometric evaluation of calcium ion release from different calcium hydroxide preparations: An in-vitro study. *Journal of Oral Research*. 2017;6(3):61-63. doi:10.17126/joralres.2017.021
16. Ordinola-Zapata R, Bramante CM, García-godoy F, Moldauer BI, Minotti PG, TerciLIA Grizzo L, et al. The effect of radiopacifiers agents on pH, calcium release, radiopacity, and antimicrobial properties of different calcium hydroxide dressings. *Microsc Res Tech*. 2015;78(7):620-625. doi:10.1002/jemt.22521
17. Sidiqa AN, Zakaria MN, Artilia I, Dewi ZY, Cahyanto A. Evaluation of calcium ion release in calcium hydroxide prototype as intracanal medicament. *Journal of Dentomaxillofacial Science*. 2020;5(2):86. doi:10.15562/jdmfs.v0i0.1017
18. Orucoglu H, Cobankara FK. Effect of unintentionally extruded calcium hydroxide paste including barium sulfate as a radiopaquing agent in treatment of teeth with periapical lesions: report of a case. *J Endod*. 2008;34(7):888-891. doi:10.1016/j.joen.2008.04.012.

19. Guerreiro-Tanomaru JM, Cornélio ALG, Andolfatto C, Salles LP, Tanomaru-Filho M. pH and Antimicrobial Activity of Portland Cement Associated with Different Radiopacifying Agents. *ISRN Dent.* 2012;12:1-5. doi:10.5402/2012/469019.
20. Taglieri G, Mondelli C, Daniele V, Pusceddu E, Trapananti A. Synthesis and X-Ray Diffraction Analyses of Calcium Hydroxide Nanoparticles in Aqueous Suspension. *Advances in Materials Physics and Chemistry.* 2013;03(01):108-112. doi:10.4236/ampc.2013.31A013.
21. Samiei M, Farjami A, Dizaj SM, Lotfipour F. Nanoparticles for antimicrobial purposes in Endodontics: A systematic review of in vitro studies. *Materials Science and Engineering: C.* 2016;58:1269-1278. doi:10.1016/j.msec.2015.08.070.